

pH-Responsive Nanoparticles for Drug Delivery

Weiwei Gao,^{†,‡} Juliana M. Chan,[§] and Omid C. Farokhzad^{*,†,||}

Laboratory of Nanomedicine and Biomaterials, Department of Anesthesiology, Brigham and Women's Hospital, Boston, Massachusetts 02115, United States, and Division of Health Science and Technology and Department of Biology, Massachusetts Institute of Technology, Cambridge, Massachusetts 02139, United States

Received August 1, 2010; Revised Manuscript Received September 7, 2010; Accepted September 13, 2010

Abstract: First-generation nanoparticles (NPs) have been clinically translated as pharmaceutical drug delivery carriers for their ability to improve on drug tolerability, circulation half-life, and efficacy. Toward the development of the next-generation NPs, researchers have designed novel multifunctional platforms for sustained release, molecular targeting, and environmental responsiveness. This review focuses on environmentally responsive mechanisms used in NP designs, and highlights the use of pH-responsive NPs in drug delivery. Different organs, tissues, and subcellular compartments, as well as their pathophysiological states, can be characterized by their pH levels and gradients. When exposed to these pH stimuli, pH-responsive NPs respond with physicochemical changes to their material structure and surface characteristics. These include swelling, dissociating or surface charge switching, in a manner that favors drug release at the target site over surrounding tissues. The novel developments described here may revise the classical outlook that NPs are passive delivery vehicles, in favor of responsive, sensing vehicles that use environmental cues to achieve maximal drug potency.

Keywords: Nanoparticles; drug delivery; responsive; pH; acid

1. Introduction

In the past decade, a myriad of nanoparticle (NP)-based drug delivery systems have been used for clinical applications that range from oncologic to cardiovascular disease.^{1,2} These nanomedicines improve existing treatments through their altered pharmacokinetics and biodistribution profiles. To further improve on NP therapeutic efficacy, researchers have explored the use of environmentally responsive NPs that can, when exposed to external stimuli, produce physicochemical

changes that favor drug release at the target site.³ These external stimuli include (i) physical signals such as temperature, electric field, magnetic field, and ultrasound; and (ii) chemical signals such as pH, ionic strength, redox potential, and enzymatic activities. NP systems that include liposomes, polymeric micelles, lipoplexes, and polyplexes have been developed to use these physical and chemical cues to modify drug release properties.^{4,5}

* Corresponding author. E-mail: ofarokhzad@zeus.bwh.harvard.edu.
Tel: 617-732-6093. Fax: 617-264-6378. Mailing address:
Laboratory of Nanomedicine and Biomaterials, Department
of Anesthesiology, Brigham and Women's Hospital, Harvard
Medical School, 75 Francis Street, Boston, MA 02115, USA.

† Brigham and Women's Hospital.

‡ Division of Health Science and Technology, Massachusetts
Institute of Technology.

§ Department of Biology, Massachusetts Institute of Technology.

|| Conflict of interest: Dr. Omid C. Farokhzad has financial interest
in BIND Biosciences and Selecta Biosciences, biopharma-
ceutical companies developing therapeutic targeted nanoparticles.

- (1) Zhang, L.; Gu, F. X.; Chan, J.; Wang, A. Z.; Langer, R.; Farokhzad, O. C. Nanoparticles in Medicine: Therapeutic Applications and Developments. *Clin. Pharmacol. Ther.* **2008**, *83*, 761–769.
- (2) Farokhzad, O. C.; Langer, R. Impact of Nanotechnology on Drug Delivery. *ACS Nano* **2009**, *3*, 16–20.
- (3) Stuart, M. A. C.; Huck, W. T. S.; Genzer, J.; Müller, M.; Ober, C.; Stamm, M.; Sukhorukov, G. B.; Szleifer, I.; Tsukruk, V. V.; Urban, Winnik, F.; Zauscher, S.; Luzinov, I.; Minko, S. Emerging Applications of Stimuli-Responsive Polymer Materials. *Nat. Mater.* **2010**, *9*, 101–113.
- (4) Muthu, M. S.; Rajesh, C. V.; Mishra, A.; Singh, S. Stimulus-Responsive Targeted Nanomicelles for Effective Cancer Therapy. *Nanomedicine* **2009**, *4*, 657–667.

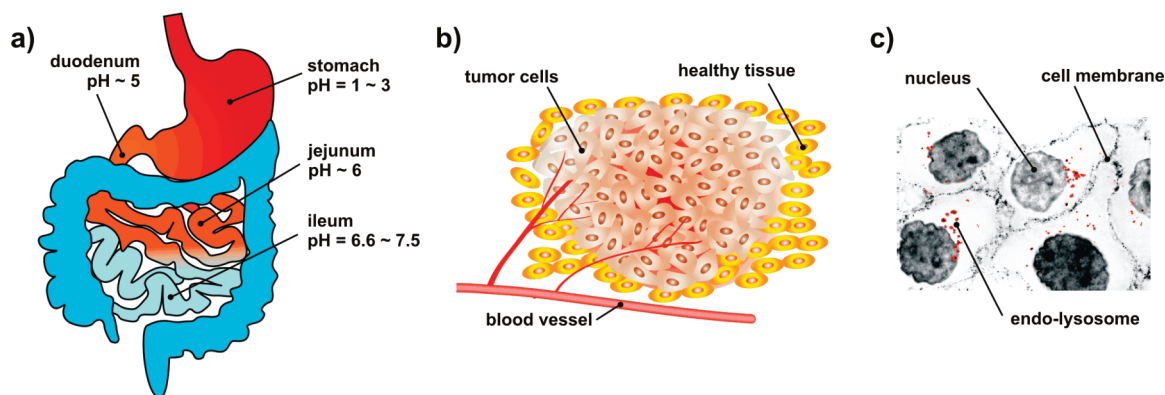


Figure 1. Design of acid-responsive NPs for selective drug release. (a) Targeting at the organ level: the GI tract is characterized by a pH gradient. (b) Targeting at the tissue level: solid tumors have a characteristic acidic extracellular environment different from healthy tissues. (c) Targeting at the cellular level: endolysosomes are more acidic in comparison to the cytoplasm (shown in red).

Among these environmental stimuli, pH gradients have been widely used to design novel, responsive NPs. This review assesses pH-responsive NP-based drug delivery at three levels, namely, at the level of (i) organs and (ii) tissues and (iii) subcellular compartments (Figure 1). In particular, we will take specific examples from oral drug delivery, tumor targeting, and intracellular delivery to highlight conceptually interesting pH-responsive NP designs. At the organ level, NP-based oral delivery systems have been formulated for differential drug uptake along the gastrointestinal (GI) tract (Figure 1a).^{6,7} At the tissue level, NP formulations have been designed to exploit the pH gradients that exist in tumor microenvironments to achieve high local drug concentrations (Figure 1b).^{8,9} Finally, at the intracellular level, pH-responsive NPs have been designed to escape acidic endolysosomal compartments for cytoplasmic drug release (Figure 1c).^{10,11}

Hence, NP formulations that respond to pH gradients within the microenvironments of organs, tissues, and cell organelles may be useful additions to the spectrum of NP-based vehicles available for therapeutic drug delivery.

2. pH-Responsive Drug Delivery at the Organ Level: Oral Drug Delivery

Each segment of the gastrointestinal (GI) tract maintains its own characteristic pH level, from the acidic stomach lumen (pH 1–3) for digestion,¹² to the alkaline duodenum and ileum (pH 6.6–7.5) for the neutralization of chyme.^{13,14} Oral delivery is an attractive drug delivery route for its convenience, patient compliance, and cost-effectiveness. However, orally delivered drugs are exposed to strong gastric acid and presystemic enzymatic degradation, resulting in poor systemic exposure. Therefore, it has proven to be a challenge to achieve adequate and consistent bioavailability levels for orally administered drugs.^{15,16} Until now, NPs formulated with biodegradable polymers have been used to improve bioavailability of easily degraded peptide drugs such as insulin,^{17,18} calcitonin,¹⁹ and elcotonin.²⁰ More recently,

(5) Li, Y. Y.; Dong, H. Q.; Wang, K.; Shi, D. L.; Zhang, X. Z.; Zhuo, R. X. Stimulus-Responsive Polymeric Nanoparticles for Biomedical Applications. *Sci. China Chem.* **2010**, *53*, 447–457.

(6) Rajput, G.; Majmudar, F.; Patel, J.; Thakor, R.; Rajgor, N. B. Stomach-Specific Mucoadhesive Microsphere as a Controlled Drug Delivery System. *Syst. Rev. Pharm.* **2010**, *1*, 70–78.

(7) Davis, S. S.; Wilding, E. A.; Wilding, I. R. Gastrointestinal Transit of a Matrix Tablet Formulation: Comparison of Canine and Human Data. *Int. J. Pharm.* **1993**, *94*, 235–238.

(8) Asokan, A.; Cho, M. J. Exploitation of Intracellular pH Gradient in the Cellular Delivery of Macromolecules. *J. Pharm. Sci.* **2002**, *91*, 903–913.

(9) Gerweck, L. E.; Vijayappa, S.; Kozin, S. Tumor pH Controls the in Vivo Efficacy of Weak Acid and Base Chemotherapeutics. *Mol. Cancer Ther.* **2006**, *5*, 1275–1279.

(10) Whitehead, K. A.; Langer, R.; Anderson, D. G. Knocking Down Barriers: Advances in SiRNA Delivery. *Nat. Rev. Drug Discovery* **2009**, *8*, 129–138.

(11) Dominska, M.; Dykxhoorn, D. M. Breaking Down the Barriers: SiRNA Delivery and Endosome Escape. *J. Cell. Sci.* **2010**, *123*, 1183–1189.

(12) Dressman, J. B.; Berardi, R. R.; Dermentzoglou, L. C.; Russell, T. L.; Schmaltz, S. P.; Barnett, J. L.; Jarvenpaa, K. M. Upper Gastrointestinal (GI) pH in Young, Healthy Men and Women. *Pharm. Res.* **1990**, *7*, 756–761.

(13) Read, N. W.; Sugden, K. Gastrointestinal Dynamics and Pharmacology for the Optimum Design of Controlled-Release Oral Dosage Forms. *Crit. Rev. Ther. Drug Carrier Syst.* **1998**, *4*, 221–263.

(14) Kararli, T. T. Comparison of the Gastrointestinal Anatomy, Physiology, and Biochemistry of Humans and Commonly Used Laboratory Animals. *Biopharm. Drug Dispos.* **1995**, *16*, 351–380.

(15) Morishita, M.; Peppas, N. A. Is the Oral Route Possible for Peptide and Protein Drug Delivery. *Drug Discovery Today* **2006**, *11*, 905–910.

(16) Yamanaka, Y. J.; Leong, K. W. Engineering Strategies to Enhance Nanoparticle-Mediated Oral Delivery. *J. Biomater. Sci., Polym. Ed.* **2008**, *19*, 1549–1570.

(17) Delie, F.; Blanco-Prieto, M. J. Polymeric Particulates to Improve Oral Bioavailability of Peptide Drugs. *Molecules* **2005**, *10*, 65–80.

(18) Sarmiento, B.; Ribeiro, A.; Veiga, F.; Ferreira, D.; Neufeld, R. Oral Bioavailability of Insulin Contained in Polysaccharide Nanoparticles. *Biomacromolecules* **2007**, *8*, 3054–3060.

(19) Lamprecht, A.; Yamamoto, H.; Takeuchi, H.; Kawashima, Y. pH-Sensitive Microsphere Delivery Increases Oral Bioavailability of Calcitonin. *J. Controlled Release* **2004**, *98*, 1–9.

newer nanomedicines have included pH-responsive mechanisms to improve systemic exposure via greater gastric retention, transepithelial transport, and cellular targeting with surface-functionalized ligands.^{21,22}

One widely adopted approach to achieve organ-specific drug release is to formulate NPs that exhibit pH-dependent swelling. For example, when acrylic-based polymers such as poly(methacrylic acid) (PMAA) are used, NPs retain a hydrophobic, collapsed state in the stomach due to the protonation of carboxyl groups. After gastric passage, an increase in pH leads to NP swelling due to carboxyl ionization and hydrogen bond breakage.²¹ Based on these properties, PMAA-poly(ethylene glycol) (PEG) diblock copolymers were able to achieve swelling ratios (mass of swollen polymer/mass of dry polymer) of 40–90-fold depending on copolymer composition and PEG graft length.²³ When NPs were loaded with insulin, ~90% of the insulin was released at pH 7.4 within two hours in their swollen state, whereas only a small fraction (approximately 10%) of the insulin was released at pH 1.2 in their collapsed state.

In addition, PMAA copolymers that contain other components such as polyethylacrylate (PMAA-PEA) and poly-methacrylate (PMAA-PMA) show pH-dependent dissolution that may be tailored to respond to the pH of different intestinal regions.²⁴ For example, Eudragit L100-55, a commercial formulation of PMAA-PEA, dissolves at pH >5.5 and is therefore suitable for duodenal drug release. Similarly, Eudragit S100, a commercial formulation of PMAA-PMA, dissolves at pH >7.0 and is suitable for ileal drug release.²⁵

Researchers have designed NPs that undergo a surface charge reversal after gastric passage to promote drug release in the alkaline intestinal tract. Using inorganic materials such as mesoporous silica, NPs were surface-functionalized with different densities of positively charged trimethylammonium (TA) functional groups.²⁶ The positively charged TA facili-

tated loading of anionic drugs such as sulfasalazine (an anti-inflammatory prodrug for bowel disease) in acidic environments (pH <3). When the drug-loaded NPs were placed in physiological buffers (pH 7.4), a partial negative surface charge on the NPs was generated from the deprotonation of silanol groups; this electrostatic repulsion triggered the sustained release of loaded molecules.

pH-responsive NPs have been used to preferentially release drugs at sites of disease. Heparin-chitosan NPs were formulated to treat *Helicobacter pylori* infections, given that the mucus layer and epithelium of the gastric lumen has a higher pH than the overall acidic environment of the stomach.²⁷ 130–300 nm NPs were self-assembled by the mixing of heparin and chitosan at pH 1.2–2.5; the NPs were stable in the gastric lumen attributable to electrostatic interactions within the structures. Upon contact with an *H. pylori* infection along the gastric epithelium (pH ~7.4), the deprotonation of chitosan occurred, which weakened electrostatic interactions and led to NP collapse and heparin release. In another study, chitosan, together with poly- γ -glutamic acid, tripolyphosphate, and MgSO₄, was used to formulate “multi-ion-cross-linked” NPs. The NPs were used to encapsulate insulin at pH <6 and release it at higher pH by chitosan deprotonization and NP destabilization.²⁸

NPs have been surface-modified with selective targeting ligands for differential retention along the GI tract. The ligands used in these studies are acid-stable and include lectin,²⁹ small peptides^{30,31} and vitamins.^{32,33} For example, chitosan, which has been shown to facilitate particle transcytosis across the intestinal epithelium, was used to

- (20) Kawashima, Y.; Yamamoto, H.; Takeuchi, H.; Kuno, Y. Mucoadhesive DI-Lactide/Glycolide Copolymer Nanospheres Coated with Chitosan to Improve Oral Delivery of Elcatonin. *Pharm. Dev. Technol.* **2000**, *5*, 77–85.
- (21) Colombo, P.; Sonvico, F.; Colombo, G.; Bettini, R. Novel Platforms for Oral Drug Delivery. *Pharm. Res.* **2009**, *26*, 601–611.
- (22) Roger, E.; Lagarce, F.; Garcion, E.; Benoit, J. Biopharmaceutical Parameters to Consider in Order to Alter the Fate of Nanocarriers after Oral Delivery. *Nanomedicine* **2010**, *5*, 287–306.
- (23) Peppas, N. A. Devices Based on Intelligent Biopolymers for Oral Protein Delivery. *Int. J. Pharm.* **2004**, *277*, 11–17.
- (24) Dai, S.; Tam, K. C.; Jenkins, R. D. Aggregation Behavior of Methacrylic Acid/Ethyl Acrylate Copolymer in Dilute Solutions. *Eur. Polym. J.* **2000**, *36*, 2671–2677.
- (25) Dai, J.; Nagai, T.; Wang, X.; Zhang, T.; Meng, M.; Zhang, Q. pH-Sensitive Nanoparticles for Improving the Oral Bioavailability of Cyclosporine A. *Int. J. Pharm.* **2004**, *280*, 229–240.
- (26) Lee, C.; Lo, L.; Mou, C.; Yang, C. Synthesis and Characterization of Positive-Charge Functionalized Mesoporous Silica Nanoparticles for Oral Drug Delivery of an Anti-Inflammatory Drug. *Adv. Funct. Mater.* **2008**, *18*, 3283–3292.

- (27) Lin, Y.; Chang, C.; Wu, Y.; Hsu, Y.; Chiou, S.; Chen, Y. Development of pH-Responsive Chitosan/Heparin Nanoparticles for Stomach-Specific Anti-*Helicobacter pylori* Therapy. *Biomaterials* **2009**, *30*, 3332–3342.
- (28) Lin, Y.; Sonaje, K.; Lin, K. M.; Juang, J.; Mi, F.; Yang, H.; Sung, H. Multi-Ion-Crosslinked Nanoparticles with pH-Responsive Characteristics for Oral Delivery of Protein Drugs. *J. Controlled Release* **2008**, *132*, 141–149.
- (29) Akande, J.; Yeboah, K. G.; Addo, R. T.; Siddig, A.; Oettinger, C. W.; D’Souza, M. J. Targeted Delivery of Antigens to the Gut-Associated Lymphoid Tissues: 2. Ex Vivo Evaluation of Lectin-Labelled Albumin Microspheres for Targeted Delivery of Antigens to the M-Cells of the Peyer’s Patches. *J. Microencapsulation* **2010**, *27*, 325–336.
- (30) Higgins, L. M.; Lambkin, I.; Donnelly, G.; Byrne, D.; Wilson, C.; Dee, J.; Smith, M.; O’Mahony, D. J. In Vivo Phage Display to Identify M Cell-Targeting Ligands. *Pharm. Res.* **2004**, *21*, 695–705.
- (31) Garinot, M.; Fiévez, V.; Pourcelle, V.; Stoffelbach, F.; Rieux, A.; Plapied, L.; Theate, I.; Freichels, H.; Jérôme, C.; Marchand-Brynaert, J.; Schneider, Y.; Prétat, V. PEGylated PLGA-Based Nanoparticles Targeting M Cells for Oral Vaccination. *J. Controlled Release* **2007**, *120*, 195–204.
- (32) Zhang, Z.; Feng, S. Self-Assembled Nanoparticles of Poly(Lactide)-Vitamin E Tpgs Copolymers for Oral Chemotherapy. *Int. J. Pharm.* **2006**, *324*, 191–198.
- (33) Chalasani, K. B.; Russell-Jones, G. J.; Jain, A. K.; Diwan, P. V.; Jain, S. K. Effective Oral Delivery of Insulin in Animal Models Using Vitamin B12-Coated Dextran Nanoparticles. *J. Controlled Release* **2007**, *122*, 141–150.

formulate PMAA-chitosan-PEG NPs.³⁴ Vitamin B-12, which enhanced NP apical-to-basal transport in Caco-2 cells,³⁵ was surface-functionalized onto dextran NPs for insulin delivery *in vivo*.³³ In addition, RGD peptides were used to target to β_1 integrins expressed on the apical side of M cells *in vitro*³⁶ and *in vivo*.³¹ Novel peptides were selected using *in vivo* phage display to identify peptides for targeted NP delivery to the M cells and follicle-associated epithelium (FAE) of the intestinal tract.³⁰

Hence, the NPs described here show pH-dependent drug release properties, enhanced membrane permeability, and have been modified with selective targeting ligands. These NPs are promising delivery vehicles for differential retention and uptake along the GI tract, and ultimately, they may improve on the efficacy of orally delivered nanomedicines.

3. pH-Responsive Mechanisms at the Tissue Level: Tumor Targeting

Human tumors have been shown to exhibit acidic pH states that range from 5.7 to 7.8 (Figure 1b).³⁷ The acidity of tumor microenvironments is caused in part by lactic acid accumulation in rapidly growing tumor cells owing to their elevated rates of glucose uptake but reduced rates of oxidative phosphorylation.³⁸ This persistence of high lactate production by tumors in the presence of oxygen, termed Warburg's effect, provides a growth advantage for tumor cells *in vivo*.³⁹ In addition, insufficient blood supply and poor lymphatic drainage, characteristics of most tumors, also contribute to the acidity of tumor microenvironment.⁴⁰ Increasingly, researchers have exploited the acidic tumor pH to achieve high local drug concentrations and to minimize overall systemic exposure.^{9,41} NPs have been formulated for pH-dependent drug release by using polymers that change their

physical and chemical properties, such as by swelling and an increase in solubility, based on local pH levels.

To achieve NP swelling, Griset et al. cross-linked NPs using acrylate-based hydrophobic polymers with hydroxyl groups that were masked by pH-labile protecting groups (e.g., 2,4,6-trimethoxybenzaldehyde).⁴² The NPs were stable at neutral pH, but the protecting group was cleaved and the hydroxyl groups were exposed at mildly acidic pH (pH ~5). This hydrophobic-to-hydrophilic transformation caused the swelling of NPs and subsequent drug release. Paclitaxel release was shown to be minimal at pH 7.4 (<10%), whereas nearly all of the paclitaxel was released within 24 h at pH 5. These acrylate-based, pH-sensitive NPs were shown to inhibit the rapid growth of LLC tumors in C57Bl/6 mice compared to nonresponsive NPs or paclitaxel in solution, suggesting that pH-responsive drug release may be beneficial for drug delivery to tumors.

pH-dependent hydrophobic-to-hydrophilic transitions may also be used to control polymer dissolution, in which the polymer matrix collapses for drug release. Wu et al. formulated NPs using PEG-poly(β -amino ester) polymers that have a pK_b of ~6.5.⁴³ At pH 6.4–6.8, amine protonation increased polymer solubility and induced a sharp micellization–demucellization transition for drug release. In another study, Criscione et al. showed that self-assembly of poly-(amidoamine) dendrimers occurred at physiological pH, followed by drug release from NP dissolution at pH <6.⁴⁴

Drug molecules have been conjugated to polymer chains via pH-labile cross-linkers for pH-responsive drug release. Recently, Aryal et al. developed cisplatin–polymer conjugated NPs using hydrazone cross-linkers to achieve low pH drug release.⁴⁵ Cisplatin release occurred at pH <6 due to hydrazone hydrolysis as opposed to poly(lactic acid) (PLA) degradation; NP uptake and subsequent cisplatin release contributed to enhanced cellular cytotoxicity over free cisplatin *in vitro*. In another study, chromone conjugated to magnetic Fe₃O₄ NPs via a Schiff-base bond led to a 4-fold improvement in chromone release at pH 5 versus at pH 7.4, an improvement in chromone solubility in buffer solutions from 2.5 to 633 $\mu\text{g/mL}$, and finally, enhanced cytotoxicity

(34) Sajeesh, S.; Sharma, C. P. Novel pH Responsive Polymethacrylic Acid-Chitosan-Polyethylene Glycol Nanoparticles for Oral Peptide Delivery. *J. Biomed. Mater. Res. B* **2006**, *76B*, 298–305.

(35) Russell-Jones, G. J.; Arthur, L.; Walker, H. Vitamin B-12-Mediated Transport of Nanoparticles across Caco-2 Cells. *Int. J. Pharm.* **1999**, *179*, 247–255.

(36) Gullberg, E.; Keita, Å. V.; Salim, S. Y.; Andersson, M.; K. D.; Caldwell; Soderholm, J. D.; Artursson, P. Identification of Cell Adhesion Molecules in the Human Follicle-Associated Epithelium That Improve Nanoparticle Uptake into the Peyer's Patches. *J. Pharmacol. Exp. Ther.* **2006**, *319*, 632–639.

(37) Vaupel, P. Tumor Microenvironmental Physiology and Its Implications for Radiation Oncology. *Semin. Radiat. Oncol.* **2004**, *14*, 198–206.

(38) Kim, J.; Dang, C. V. Cancer's Molecular Sweet Tooth and the Warburg Effect. *Cancer Res.* **2006**, *66*, 8927–8930.

(39) Christofk, H. R.; Heiden, M. G. V.; Harris, M. H.; Ramanathan, A.; Gerszten, R. E.; Wei, R.; Fleming, M. D.; Schreiber, S. L.; Cantley, L. C. The M2 splice Isoform of Pyruvate Kinase Is Important for Cancer Metabolism and Tumour Growth. *Nature* **2008**, *452*, 230–233.

(40) Brahimi-Horn, M.; Pouyssegur, J. Oxygen, a Source of Life and Stress. *FEBS Lett.* **2007**, *581*, 3582–3591.

(41) Lee, E.; Gao, Z.; B. Y. Recent Progress in Tumor pH Targeting Nanotechnology. *J. Controlled Release* **2008**, *132*, 164–170.


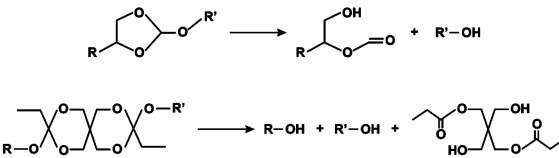

(42) Griset, A. P.; Walpole, J.; Liu, R.; Gaffey, A.; Colson, Y. L.; Grinstaff, M. W. Expansile Nanoparticles: Synthesis, Characterization, and *In Vivo* Efficacy of an Acid-Responsive Polymeric Drug Delivery System. *J. Am. Chem. Soc.* **2009**, *131*, 2469–2471.

(43) Wu, X. L.; Kim, J. H.; Koo, H.; Bae, S. M.; Shin, H.; Kim, M. S.; B.; Lee; Park, R.; Kim, I.; Choi, K.; Kwon, I. C.; Kim, K.; Lee, D. S. Tumor-Targeting Peptide Conjugated pH-Responsive Micelles as a Potential Drug Carrier for Cancer Therapy. *Bioconjugate Chem.* **2010**, *21*, 208–213.

(44) Criscione, J. M.; Le, B. L.; Stern, E.; Brennan, M.; Rahner, C.; Papademetris, X.; Fahmy, T. M. Self-Assembly of pH-Responsive Fluorinated Dendrimer-Based Particulates for Drug Delivery and Noninvasive Imaging. *Biomaterials* **2009**, *30*, 3946–3955.

(45) Aryal, S.; Hu, C. J.; Zhang, L. Polymer-Cisplatin Conjugate Nanoparticles for Acid-Responsive Drug Delivery. *ACS Nano* **2010**, *4*, 251–258.

Table 1. Common pH-Labile Cross-Linkers and Their Hydrolytic Products

Name	Structure	References
Ester	$\text{R}-\overset{\text{O}}{\parallel}{\text{C}}-\text{O}-\text{R}' \longrightarrow \text{R}-\overset{\text{O}}{\parallel}{\text{C}}-\text{OH} + \text{HO}-\text{R}'$	50,51
Hydrazone	$\text{R}'-\overset{\text{O}}{\parallel}{\text{C}}-\text{N}=\text{N}-\text{R}'' \longrightarrow \text{R}'-\overset{\text{O}}{\parallel}{\text{C}}-\text{R}'' + \text{H}_2\text{N}-\text{N}=\text{R}'$	45,52
Carboxy dimethylmaleic anhydride		49,53
Orthoester		42,48,54,55
Imine	$\text{R}-\text{N}=\text{CH}-\text{R}' \longrightarrow \text{R}-\text{NH}_2 + \text{O}=\text{CH}-\text{R}'$	46,56
β-Thiopropionate		57,58
Vinylether	$\text{R}-\text{O}-\text{CH}=\text{CH}-\text{R}' \longrightarrow \text{R}-\text{OH} + \text{O}=\text{CH}-\text{CH}_2-\text{R}'$	59,60
Phosphoramidate	$\text{R}-\text{N}-\overset{\text{O}^-}{\parallel}{\text{P}}(\text{O})-\text{O}-\text{R}' \longrightarrow \text{R}-\text{NH}_2 + \text{H}_2\text{PO}_4^- + \text{R}'-\text{OH}$	61,62

in vitro.⁴⁶ For dual-drug delivery, Shen et al. formed liposome-like NPs by conjugating camptothecin to short PEG chains via an ester bond, followed by encapsulating doxorubicin, a hydrophilic drug.⁴⁷ When loaded with doxorubicin salts (doxorubicin·HCl), rapid release of both doxorubicin and camptothecin occurred at pH <5 or when an esterase was added. Likewise, Bruyère et al. synthesized a series of orthoester model compounds which had different hydrolysis rates at pH ranging from pH 4.5 to 7.4.⁴⁸ A summary of acid labile linkers used in conjugation chemistry and their hydrolytic products are listed in Table 1.

To increase NP retention in tumors, NPs have been designed to reverse their surface charge from neutral/negative to positive at the tumor site. In one study, quantum dots and adenovirus-based NPs were surface-functionalized with pH-sensitive poly(L-lysine) (PLL).⁴⁹ PLL amine groups were conjugated with biotin-PEG and citraconic anhydride (a pH-sensitive primary amine blocker) to generate carboxylate groups. Under acidic conditions (pH <6.6), the citraconylated amide linkages were cleaved, resulting in the recovery of

- (46) Wang, B.; Xu, C.; Xie, J.; Yang, Z.; Sun, S. pH Controlled Release of Chromone from Chromone-Fe₃O₄ Nanoparticles. *J. Am. Chem. Soc.* **2008**, *130*, 14436–14437.
- (47) Shen, Y.; Jin, E.; Zhang, B.; Murphy, C. J.; Sui, M.; Zhao, J.; Wang, J.; Tang, J.; Fan, M.; Kirk, E. V.; Murdoch, W. J. Prodrugs Forming High Drug Loading Multifunctional Nanocapsules for Intracellular Cancer Drug Delivery. *J. Am. Chem. Soc.* **2010**, *132*, 4259–4265.
- (48) Bruyère, H.; Westwell, A. D.; Jones, A. T. Tuning the pH Sensitivities of Orthoester Based Compounds for Drug Delivery Applications by Simple Chemical Modification. *Bioorg. Med. Chem.* **2010**, *20*, 2200–2203.

- (49) Mok, H.; Park, J. W.; Park, T. G. Enhanced Intracellular Delivery of Quantum Dot and Adenovirus Nanoparticles Triggered by Acidic pH Via Surface Charge Reversal. *Bioconjugate Chem.* **2008**, *19*, 797–801.
- (50) Sengupta, S.; Eavarone, D.; Capila, I.; Zhao, G.; Watson, N.; Kiziltepe, T.; Sasisekharan, R. Temporal Targeting of Tumour Cells and Neovasculature with a Nanoscale Delivery System. *Nature* **2005**, *436*, 568–572.
- (51) Tong, R.; Cheng, J. Ring-Opening Polymerization-Mediated Controlled Formulation of Polylactide-Drug Nanoparticles. *J. Am. Chem. Soc.* **2009**, *131*, 4744–4754.
- (52) Banerjee, S. S.; Chen, D. Multifunctional pH-Sensitive Magnetic Nanoparticles for Simultaneous Imaging, Sensing and Targeted Intracellular Anticancer Drug Delivery. *Nanotechnology* **2008**, *19*, 505104–8.

positively charged amine groups. This surface charge reversal in turn led to enhanced NP uptake by HeLa cells.

The pH-responsive mechanisms described here draw upon a general phenomenon which is the acidity of tumor microenvironments. Here, NPs maintain stability in circulation and undergo physicochemical changes that favor localized drug release.

4. pH-Responsive NPs at the Cellular Level: Intracellular Delivery

Following endocytosis, rapid endosomal acidification (~2–3 min) occurs due to a vacuolar proton ATPase-mediated proton influx. As a result, the pH levels of early endosomes, sorting endosomes, and multivesicular bodies drop rapidly to pH <6.0.⁶³ The process of endosomal acidification can be harmful to the therapeutic molecule being delivered, especially for macromolecules such as DNA, small

interfering RNA (siRNA), and proteins. However, endosomal acidification may also be used as a trigger for endosomal escape and payload release, a mechanism hypothesized to occur via a “proton sponge” effect.⁶⁴ Here, NPs absorb protons at endosomal pH, leading to an increase in osmotic pressure inside the endosomal compartment, followed by plasma membrane disruption and NP release into the cytoplasm.

pH-sensitive polymers that buffer endosomal compartments have been grafted with other functional segments for intracellular delivery. For example, a NP platform termed Dynamic PolyConjugates (Mirus Bio LLC) has an amphipathic endosomolytic poly(vinyl ether) backbone composed of butyl and amino vinyl ethers. The NPs were used to conjugate and deliver siRNA through a reversible disulfide linkage, and included functional components such as PEG and targeting ligands. The Dynamic PolyConjugates provided effective knockdown of two endogenous liver genes, apolipoprotein B and peroxisome proliferator-activated receptor alpha (PPAR α) *in vivo*.^{53,65}

Amine-containing monomers have been used in rational syntheses of polymers that buffer pH in endosomes. For example, an amphiphilic and cationic triblock copolymer consisting of monomethoxy PEG, poly(ϵ -caprolactone) and poly(2-aminoethyl ethylene phosphate) (mPEG45-*b*-PCL100-*b*-PPEEA12) was designed for endosomal buffering and siRNA delivery.⁶⁶ The NPs were found to effectively silence GFP expression in HEK293 cells without significant cytotoxicity. In another study, Tietze et al. developed β -propiionamide-cross-linked oligoethylenimine polymers for siRNA delivery. The siRNA-encapsulated NPs knocked down nuclear Ran expression without corresponding cytotoxicity.⁶⁷ Jeong et al. developed reducible poly(amido ethylenimine) (PEI) polymers by addition copolymerization of triethylene-tetramine and cystamine bis-acrylamide. The reducible PEI NPs were used to deliver siRNA that suppressed VEGF expression in PC3 human prostate cancer cell lines with lower cytotoxicity compared to linear PEI formulations.⁶⁸

Copolymers made from pH-sensitive monomers and non-ionic monomers allow fine-tuning of polymer pK_a for improved endosomal escape. For example, using copolymers made from monomers with different pK_a (e.g., dimethylaminoethyl methacrylate and nonionic monomer 2-hydroxyethyl

- (53) Rozema, D. B.; Lewis, D. L.; Wakefield, D. H.; Wong, S. C.; Klein, J. J.; Roesch, P. L.; Bertin, S. L.; Reppen, T. W.; Chu, Q.; Blokhin, A. V.; Hagstrom, J. E.; Wolff, J. A. Dynamic Polyconjugates for Targeted *In Vivo* Delivery of SiRNA to Hepatocytes. *Proc. Natl. Acad. Sci. U.S.A.* **2007**, *104*, 12982–12987.
- (54) Liu, R.; Zhang, Y.; Zhao, X.; Agarwal, A.; Mueller, L. J.; Feng, P. pH-Responsive Nanogated Ensemble Based on Gold-Capped Mesoporous Silica through an Acid-Labile Acetal Linker. *J. Am. Chem. Soc.* **2010**, *132*, 1500–1501.
- (55) Huang, X.; Du, F.; Cheng, J.; Dong, Y.; Liang, D.; Ji, S.; Lin, S.; Li, Z. Acid-Sensitive Polymeric Micelles Based on Thermoresponsive Block Copolymers with Pendent Cyclic Orthoester Groups. *Macromolecules* **2009**, *42*, 783–790.
- (56) Gu, J.; Cheng, W.; Liu, J.; Lo, S.; Smith, D.; Qu, X.; Yang, Z. pH-Triggered Reversible “Stealth” Polycationic Micelles. *Biomacromolecules* **2008**, *9*, 255–262.
- (57) Ali, M. M.; Oishi, M.; Nagatsugi, F.; Mori, K.; Nagasaki, Y.; Kataoka, K.; Sasaki, S. Intracellular Inducible Alkylation System That Exhibits Antisense Effects with Greater Potency and Selectivity Than the Natural Oligonucleotide. *Angew. Chem., Int. Ed.* **2006**, *45*, 3136–3140.
- (58) Oishi, M.; Nagatsugi, F.; Sasaki, S.; Nagasaki, Y.; Kataoka, K. Smart Polyion Complex Micelles for Targeted Intracellular Delivery of Pegylated Antisense Oligonucleotides Containing Acid-Labile Linkages. *ChemBioChem* **2005**, *6*, 718–725.
- (59) Li, Y.; Lee, P. I. A New Bioerodible System for Sustained Local Drug Delivery Based on Hydrolytically Activated *In Situ* Macromolecular Association. *Int. J. Pharm.* **2010**, *383*, 45–52.
- (60) Xu, Z.; Gu, W.; Chen, L.; Gao, Y.; Zhang, Z.; Li, Y. A Smart Nanoassembly Consisting of Acid-Labile Vinyl Ether Peg-Dope and Protamine for Gene Delivery: Preparation and *In Vitro* Transfection. *Biomacromolecules* **2008**, *9*, 3119–3126.
- (61) Jeong, J. H.; Kim, S. W.; Park, T. G. Novel Intracellular Delivery System of Antisense Oligonucleotide by Self-Assembled Hybrid Micelles Composed of DNA/Peg Conjugate and Cationic Fusogenic Peptide. *Bioconjugate. Chem.* **2003**, *14*, 473–479.
- (62) Yang, L.; Chen, L.; Zeng, R.; Li, C.; Qiao, R.; Hu, L.; Li, Z. Synthesis, Nanosizing and *In Vitro* Drug Release of a Novel Anti-HIV Polymeric Prodrug: Chitosan-O-Isopropyl-5'-O-D4t Monophosphate Conjugate. *Bioorg. Med. Chem.* **2010**, *18*, 117–123.
- (63) Murphy, R. F.; Powers, S.; Cantor, C. R. Endosome pH Measured in Single Cells by Dual Fluorescence Flow Cytometry: Rapid Acidification of Insulin to pH 6. *J. Cell. Biol.* **1984**, *98*, 1757–1762.

- (64) Behr, J. P. The Proton Sponge: A Trick to Enter Cells the Viruses Did Not Exploit. *CHIMIA* **1997**, *51*, 34–36.
- (65) Wakefield, D. H.; Klein, J. J.; Wolff, J. A.; Rozema, D. B. Membrane Activity and Transfection Ability of Amphipathic Polycations as a Function of Alkyl Group Size. *Bioconjugate. Chem.* **2005**, *16*, 1204–1208.
- (66) Sun, T.; Du, J.; Yan, L.; Mao, H.; Wang, J. Self-Assembled Biodegradable Micellar Nanoparticles of Amphiphilic and Cationic Block Copolymer for SiRNA Delivery. *Biomaterials* **2008**, *29*, 4348–4355.
- (67) Tietze, N.; Pelisek, J.; Philipp, A.; Roedl, W.; Merdan, T.; Tarcha, P.; Ogris, M.; Wagner, E. Induction of Apoptosis in Murine Neuroblastoma by Systemic Delivery of Transferrin-Shielded SiRNA Polyplexes for Downregulation of Ran. *Oligonucleotides* **2008**, *18*, 161–174.

methacrylate), it was possible to adjust NP pH sensitivity, DNA encapsulation efficiency, and monomer toxicity to optimize transfection efficiency.⁶⁹

Biodegradable poly(β -amino ester) (PbAE) polymers contain tertiary amines that have been used for pH buffering. A combinatorial family of PbAE compounds was synthesized by parallel synthesis using amine- and acrylate-terminated monomers in a Michael addition reaction, without the use of specialized monomers or protection steps.⁷⁰ In this study, PbAE NPs were shown to undergo rapid dissolution in acidic microenvironments (pH 6.5) which facilitated drug release. NPs based on PbAE have been applied to deliver small molecule drugs,⁷¹ DNA,⁷² and siRNA.^{73,74}

Stealth PEG layers that are stable in circulation but are released in endosomes have been used to facilitate NP endosomal escape. While PEG shedding itself does not cause endosomal disruption, it may aid NP escape by reducing steric and electrostatic hindrance from the PEG layer. Several PEG-sheddable NP formulations have been developed where PEG is grafted onto NPs via pH labile cross-linkers.⁷⁵ In these studies, PEG shedding was shown to both favor drug release⁷⁶ and gene expression,⁷⁷ suggesting a general application for PEG-shedding strategies.

Finally, NP designs may contain protein transduction domains (PTDs), which are cationic, 10–30 amino acid sequences hypothesized to disrupt endosomal membranes

Table 2. Summary of pH-Responsive Mechanisms Used in Nanoparticle Designs

mechanisms	references
At the Organ Level: Oral Drug Delivery	
pH-dependent swelling and dissolution (at higher pH)	21, 23–25
pH-dependent drug release “cap” (in porous silica nanoparticles)	26
pH-dependent drug dissociation and release	27, 28
At the Tissue Level: Tumor Targeting	
pH-dependent swelling and dissolution (at lower pH)	42–44
pH-sensitive drug–polymer conjugates	45–48
pH-dependent charge reversal to increase tumor retention	49
At the Cellular Level: Intracellular Delivery	
pH-sensitive polymer for endosomal buffering	53, 65–74
pH-labile linker to shed the stealth coating	75–77
pH-dependent cell penetration peptide	78–82

upon endosomal acidification.⁷⁸ The mechanism of PTD membrane penetration is an active research topic, and PTDs have been widely used to improve intracellular delivery in oncologic-based applications.^{79–81} In one study, the coadministration of a free tumor-penetrating peptide (e.g., iRGD sequence) was shown to enhance the efficacy of doxorubicin (doxorubicin liposomes), paclitaxel (nab-paclitaxel), and monoclonal antibody (trastuzumab) treatments.⁸²

However, caution must be taken when targeting is used to improve intracellular delivery, because the extent of endosomal acidification is influenced by the choice of targeting ligand used and hence the endocytic pathway taken. For example, surface modification with folate was shown to lead to endocytosis through recycling centers characterized by near neutral pH of pH 6–7, which may make it less suitable for pH-based mechanisms.⁸³

Hence, pH-sensitive mechanisms are also important at the stages after NPs internalized by the target cell, especially

- (68) Jeong, J. H.; Christensen, L. V.; Yockman, J. W.; Zhong, Z.; Engbersen, J. F. J.; Kim, W. J.; Feijen, J.; Kim, S. W. Reducible Poly(Amido Ethylenimine) Directed to Enhance Rna Interference. *Biomaterials* **2007**, *28*, 1912–1917.
- (69) You, J.; Auguste, D. T. Nanocarrier Cross-Linking Density and pH Sensitivity Regulate Intracellular Gene Transfer. *Nano Lett.* **2009**, *9*, 4467–4473.
- (70) Little, S. R.; Kohane, D. S. Polymers for Intracellular Delivery of Nucleic Acids. *J. Mater. Chem.* **2008**, *18*, 832–841.
- (71) Ko, J.; Park, K.; Kim, Y.; Kim, M. S.; Han, J. K.; Kim, K.; Park, R.; Kim, I.; Song, H. K.; Lee, D. S.; Kwon, I. C. Tumoral Acidic Extracellular pH Targeting of pH-Responsive MPEG-Poly (β -Amino Ester) Block Copolymer Micelles for Cancer Therapy. *J. Controlled Release* **2007**, *123*, 109–115.
- (72) Little, S. R.; Lynn, D. M.; Ge, Q.; Anderson, D. G.; Puram, S. V.; Chen, J.; Eisen, H. N.; Langer, R. Poly- β Amino Ester-Containing Microparticles Enhance the Activity of Nonviral Genetic Vaccines. *Proc. Natl. Acad. Sci. U.S.A.* **2004**, *101*, 9534–9539.
- (73) Tseng, S.; Tang, S. Development of poly(amino ester glycol urethane)/siRNA Polyplexes for Gene Silencing. *Bioconjugate Chem.* **2007**, *18*, 1383–1390.
- (74) Jere, D.; Xu, C.; Arote, R.; Yun, C.; Cho, M.; Cho, C. Poly(B-Amino Ester) as a Carrier for si/shRNA Delivery in Lung Cancer Cells. *Biomaterials* **2008**, *29*, 2535–2547.
- (75) Romberg, B.; Hennink, W. E.; Storm, G. Sheddable Coatings for Long-Circulating Nanoparticles. *Pharm. Res.* **2008**, *25*, 55–71.
- (76) Cerritelli, S.; Velluto, D.; Hubbell, J. A. PEG-SS-PPS: Reduction-Sensitive Disulfide Block Copolymer Vesicles for Intracellular Drug Delivery. *Biomacromolecules* **2007**, *8*, 1966–1972.
- (77) Takae, S.; Miyata, K.; Oba, M.; Ishii, T.; Nishiyama, N.; Itaka, K.; Yamasaki, Y.; Koyama, H.; Kataoka, K. Peg-Detachable Polyplex Micelles Based on Disulfide-Linked Block Cationomers as Bioresponsive Nonviral Gene Vectors. *J. Am. Chem. Soc.* **2008**, *130*, 6001–6009.

- (78) Lundberg, M.; Wikstrom, S.; Johansson, M. Cell Surface Adherence and Endocytosis of Protein Transduction Domains. *Mol. Ther.* **2003**, *8*, 143–150.
- (79) Lindgren, M.; Hällbrink, M.; Prochiantz, A.; Langel, Ü. Cell-Penetrating Peptides. *TiPS* **2000**, *21*, 99–103.
- (80) Gupta, B.; Levchenko, T. S.; Torchilin, V. P. Intracellular Delivery of Large Molecules and Small Particles by Cell-Penetrating Proteins and Peptides. *Adv. Drug Delivery Rev.* **2005**, *57*, 637–651.
- (81) Meade, B. R.; Dowdy, S. F. Enhancing the Cellular Uptake of siRNA Duplexes Following Noncovalent Packaging with Protein Transduction Domain Peptides. *Adv. Drug Delivery Rev.* **2008**, *60*, 530–536.
- (82) Sugahara, K. N.; Teesalu, T.; Karmali, P. P.; Kotamraju, V. R.; Agemy, L.; Greenwald, D. R.; Ruoslahti, E. Coadministration of a Tumor-Penetrating Peptide Enhances the Efficacy of Cancer Drugs. *Science* **2010**, *328*, 1031–1035.

for cytoplasmic release of a payload. These mechanisms are even more crucial for payloads such as siRNA, DNA, and proteins, where denaturation in the acidic lysosomal compartment may result in a significant loss of efficacy.

5. Concluding Remarks

Novel approaches in pH-responsive NP design and engineering have resulted in improvements to drug delivery at the preclinical stage. In this paper, we have reviewed recent progress made in the research and development of pH-

responsive NPs for drug delivery at three levels: at the organ, tissue and subcellular levels. The mechanisms employed in these studies are summarized in Table 2. With sustained effort in tailoring NPs for environmentally sensitive drug delivery, it is expected that environmentally responsive approaches will result in next-generation nanomedicines that have extensive medical applications.

Acknowledgment. Authors' research was supported by National Institutes of Health Grants CA119349 and EB003647 and Koch-Prostate Cancer Foundation Award in Nanotherapeutics. JMC acknowledges financial support from the Agency of Science, Technology and Research (A*STAR), Singapore.

MP100253E

-
- (83) Yang, J.; Chen, H.; Vlahov, I. R.; Cheng, J.; Low, P. S. Characterization of the pH of Folate Receptor-Containing Endosomes and the Rate of Hydrolysis of Internalized Acid-Labile Folate-Drug Conjugates. *J. Pharmacol. Exp. Ther.* **2007**, *321*, 462–468.